

AFRL-ML-WP-TP-2007-526

**ON THE STRUCTURE OF
HOLOGRAPHIC POLYMER
DISPERSED POLYETHYLENE
GLYCOL (Preprint)**



**Timothy J. Bunning, Michael J. Birnkrant, Hillary McWilliams,
Christopher Y. Li, Lalgudi V. Natarajan, Vincent P. Tondiglia,
Richard L. Sutherland, and Pamela F. Lloyd**

OCTOBER 2006

Approved for public release; distribution unlimited.

STINFO COPY

The U.S. Government is joint author of this work and has the right to use, modify, reproduce, release, perform, display, or disclose the work.

**MATERIALS AND MANUFACTURING DIRECTORATE
AIR FORCE RESEARCH LABORATORY
AIR FORCE MATERIEL COMMAND
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7750**

NOTICE

Using Government drawings, specifications, or other data included in this document for any purpose other than Government procurement does not in any way obligate the U.S. Government. The fact that the Government formulated or supplied the drawings, specifications, or other data does not license the holder or any other person or corporation; or convey any rights or permission to manufacture, use, or sell any patented invention that may relate to them.

This report was cleared for public release by the Air Force Research Laboratory Wright Site (AFRL/WS) Public Affairs Office (PAO) and is releasable to the National Technical Information Service (NTIS). It will be available to the general public, including foreign nationals.

THIS TECHNICAL REPORT IS APPROVED FOR PUBLICATION.

*//signature//

TIMOTHY J. BUNNING, Ph.D.
Research Lead
Exploratory Development
Hardened Materials Branch

//signature//

MARK S. FORTE, Acting Chief
Hardened Materials Branch
Survivability and Sensor Materials Division

//signature//

TIM J. SCHUMACHER Chief
Survivability and Sensor Materials Division

This report is published in the interest of scientific and technical information exchange and its publication does not constitute the Government's approval or disapproval of its ideas or findings.

*Disseminated copies will show “//signature//” stamped or typed above the signature blocks.

REPORT DOCUMENTATION PAGE					<i>Form Approved OMB No. 0704-0188</i>	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.						
1. REPORT DATE (DD-MM-YY) October 2006		2. REPORT TYPE Journal Article Preprint		3. DATES COVERED (From - To)		
4. TITLE AND SUBTITLE ON THE STRUCTURE OF HOLOGRAPHIC POLYMER DISPERSED POLYETHYLENE GLYCOL (Preprint)				5a. CONTRACT NUMBER IN-HOUSE		
				5b. GRANT NUMBER		
				5c. PROGRAM ELEMENT NUMBER 62102F		
6. AUTHOR(S) Timothy J. Bunning (Exploratory Development, Hardened Materials Branch) Michael J. Birnkrant, Hillary McWilliams, and Christopher Y. Li (Drexel University) Lalgudi V. Natarajan, Vincent P. Tondiglia, and Richard L. Sutherland (SAIC) Pamela F. Lloyd (UES, Inc.)				5d. PROJECT NUMBER 4347		
				5e. TASK NUMBER RG		
				5f. WORK UNIT NUMBER M08R1000		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) <div style="display: flex; justify-content: space-between;"> <div style="width: 45%;"> Exploratory Development, Hardened Materials Branch Survivability and Sensor Materials Division Materials and Manufacturing Directorate Air Force Research Laboratory Wright-Patterson Air Force Base, OH 45433-7750 </div> <div style="width: 45%;"> - SAIC - Drexel University - UES </div> </div>				8. PERFORMING ORGANIZATION REPORT NUMBER AFRL-ML-WP-TP-2007-526		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Materials And Manufacturing Directorate Air Force Research Laboratory Air Force Materiel Command Wright-Patterson Air Force Base, OH 45433-7750				10. SPONSORING/MONITORING AGENCY ACRONYM(S) AFRL/MLPJ 11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S) AFRL-ML-WP-TP-2007-526		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.						
13. SUPPLEMENTARY NOTES The U.S. Government is joint author of this work and has the right to use, modify, reproduce, release, perform, display, or disclose the work. PAO case number AFRL/WS 06-2299, 27 September 2006. Submitted for publication to Polymer. This is the best quality available.						
14. ABSTRACT Holographic polymerization (H-P) has been used to fabricate polymer dispersed liquid crystals and pattern inert nanoparticles. In this article, one-dimensional grating structures of Norland resin and polyethylene glycol (PEG) was achieved using the H-P technique. Both reflection and transmission grating structures were fabricated. The optical properties of the reflection grating structures (also known as Bragg reflectors (BRs)) are thermosensitive, which can be attributed to the formation and crystallization of PEG crystals. The thermal switching temperature of the BR can be tuned by using different molecular weight PEG samples. The hierarchical structure and morphology of the BR were studied using synchrotron X-ray, polarized light microscopy, and transmission electron microscopy. PEG crystals were found to be confined in ~60 nmthick layers in the BR. Upon crystallization, the PEG lamellae were parallel to the BR surfaces and PEG chains were parallel to the BR normal, resembling the confined crystallization behavior of polyethylene oxide (PEO) in PEO-block-polystyrene (PEO-b-PS) block copolymers. This observation suggests that the tethering effect in the block copolymer systems does not play a major role in PEG chain orientation in the confined nanoenvironment.						
15. SUBJECT TERMS Bragg Reflectors (BRs), Polyethylene oxide (PEO), Polyethylene glycol (PEG)						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT: SAR	18. NUMBER OF PAGES 30	19a. NAME OF RESPONSIBLE PERSON (Monitor) Timothy J. Bunning, Ph.D.	
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include Area Code) (937) 255-4588	

On the Structure of Holographic Polymer Dispersed Polyethylene Glycol

Michael J. Birnkrant, Hillary McWilliams, Christopher Y. Li,*

A. J. Drexel Nanotechnology Institute and Department of Materials Science and Engineering

Drexel University, Philadelphia, PA 19104

Email: Chrisli@drexel.edu

Lalgudi V. Natarajan, Vincent P. Tondiglia, Richard L. Sutherland,

Science Applications International Corporation

4031 Colonel Glenn Highway, Dayton, OH 45431

Pamela F. Lloyd,

UES, Inc., 4401 Dayton-Xenia Rd. Dayton, OH 45432

Timothy J. Bunning*

Air Force Research Laboratory, Materials & Manufacturing Directorate, Wright-Patterson Air

Force Base, OH 45433

ABSTRACT:

Holographic polymerization (H-P) has been used to fabricate polymer dispersed liquid crystals and pattern inert nanoparticles. In this article, one dimensional grating structures of Norland resin and polyethylene glycol (PEG) was achieved using the H-P technique. Both reflection and

transmission grating structures were fabricated. The optical properties of the reflection grating structures (also known as Bragg reflectors BRs) are thermosensitive, which can be attributed to the formation and crystallization of PEG crystals. The thermal switching temperature of the BR can be tuned by using different molecular weight PEG samples. The hierarchical structure and morphology of the BR were studied using synchrotron X-ray, polarized light microscopy and transmission electron microscopy. PEG crystals were found to be confined in ~60 nm thick layers in the BR. Upon crystallization, the PEG lamellae were parallel to the BR surfaces and PEG chains were parallel to the BR normal, resembling the confined crystallization behavior of polyethylene oxide (PEO) in PEO-block-polystyrene (PEO-b-PS) block copolymers. This observation suggests that the tethering effect in the block copolymer systems does not play a major role in PEG chain orientation in the confined nanoenvironment.

INTRODUCTION:

A number of different methods, including colloid crystal assembly lithography technique and block copolymer (BCP) self-assembly, have been used to fabricate wavelength scale photonic structures in order to mold the flow of light. (1-5) A drawback of these techniques is the required lengthy sample preparation. In the latter case, defects inherent in BCPs hinder the formation of large-scale, pristine, structures although a number of methods have been proposed. (6-9) Recently, holographic photopolymerization (H-P) has been proven to be a simple, fast and attractive means to fabricate one-, two- and three-dimensional (1D, 2D, 3D) complex photonic structures at a relatively large scale. (10) During the H-P process, a photopolymerizable syrup is exposed to two or more coherent, interfering laser beams, which create a standing wave pattern. Higher intensity regions within the standing wave result in a locally faster polymerization process, which leads to a spatial distribution of high molecular weight (Mw) polymers. Pure polymer films with a periodic refractive index (RI) modulation normal to the film surface (reflection geometry) were first fabricated several decades ago. (11-13) This unique technique was extended in the mid-90's by including low molar mass, anisotropic liquid crystals (LCs) in the polymerization syrup. Non-reactive LCs, normally ~20-30 (w/w)% of the syrup, are mixed with photopolymerizable monomers, initiators and surfactants. H-P of this mixture leads to periodically patterned, nanoscale LC droplets, a structure known as holographic polymer-dispersed liquid crystals (HPDLC). (10) The RI contrast can be easily controlled by applying external electric fields and the optical properties of HPDLC can thus be modulated. Novel 3D photonic crystal structures were also formed by using a multiple-beam set-up. (14-17)

Due to the fast kinetics of photopolymerization, these holographic structures can be fabricated within seconds and the symmetry, dimensionality, size and RI modulation can be

easily controlled by the fabrication conditions. In addition to patterning LCs, a variety of nanosized objects have also been patterned into ordered photonic structures.⁽¹⁸⁾ In theory, if the nanosize objects do not affect the polymerization process, they could be patterned into ordered structures using the H-P method. However, phase separation during the photopolymerization process is rather complicated and often times, the rate of phase separation between the crosslinked resins/monomers and the to-be-patterned objects has to occur in a similar rate as photopolymerization. Miscibility and viscosity dictate the phase separation kinetics, which, in turn, account for the formation of the ordered nanostructures. By replacing the LC with gold nanoparticles (5 nm in diameter), polystyrene (PS), latex spheres (260 nm diameter) or silicate nanoplates, H-P led to 1D structures with spatially patterned nanoparticles and the periodicity is approximately a few hundreds nanometers.⁽¹⁸⁾

We recently investigated reflection grating structures—BR—formed by H-P of a syrup containing photopolymerizable monomers (Norland resin), initiators and an inert polymer, polyethylene glycol (PEG).⁽¹⁹⁾ Using PEG to replace previously reported LC/nanoparticles, uniform 1D BR structures could also be formed, although PEG molecules are much larger in size than that of small molecular mass LCs. The grating was formed due to the lamellar ordering of crosslinked Norland resin and semi-continuous layers of PEG. Interestingly, the reflecting wavelength red shifts approximately twenty nanometers while the DE concurrently increases upon heating. This thermoswitching behavior was attributed to the PEG crystal formation and melting during the cooling and heating processes. The structure and crystallization behavior of PEG BR are investigated in this paper. PEG/Norland BR with different Mw PEG samples thermally switched and transmission optical structures of PEG/Norland were also fabricated. The transition temperature depends on the PEG Mw. Detailed synchrotron X-ray studies show that

the holographic polymer dispersed polymer (HPDP) structure provides nanoconfinement during the PEG crystal structure formation. All the PEG crystals confined by HPDP investigated contained PEG chains that are exclusively parallel to the BR normal. Comparisons of the HPDP structure with the previously investigated nanoconfined crystallization of PEO in block copolymers are discussed.

EXPERIMENTAL

Materials

The formulation of the prepolymer syrup consisted of 15-30 (w/w) % PEG, 65-80% crosslinkable monomer and 3-5% photoinitiators. PEG with MW 2000, 4600, 8000 g/mol were purchased from Aldrich Co.. The crosslinkable polymer was a commercially available thiol-ene polymer known as Norland Optical Adhesive 65 and Norland Blocking Adhesive 107 from Norland Products Inc.. The photoinitiator was Darocure© 4265 from CIBA-GEIGY company. All materials were used as received.

Formation of Holographic Bragg Grating

The fabrication of reflection gratings was achieved using a Coherent Ar-ion laser (model Sabre Innova 10R/2) with a laser wavelength of 363.8 nm and an output power of ~ 300 mW using a single beam configuration as shown in Figure 1a. The interference pattern that arises from the internal reflection of the beam on the hypotenuse of an isosceles 90° glass prism results in the formation of a grating. The cell was placed in optical contact with the prism hypotenuse using an index-matching fluid and the exposure time was typically 30-60s. The prism and the cell assembly were placed on a rotation stage to change the notch wavelength. Transmission

gratings can also be obtained in the present system; the laser set-up for the transmission grating writing is shown in Figure 1b. A diffuse UV laser was split into two beams using the prism and these beams were converged on the BR cell forming a grating.

Characterization

Bright-field transmission electron microscopy (BFTEM) was performed on a JEOL 2000FX TEM with an accelerating voltage of 120 kV. A Reichert Ultracut cryo-ultramicrotome was used to microtome the BR sample with a DiATOME 35° diamond knife. 60nm thin sections of the sample were cut and floated on the water surface and subsequently collected on a TEM copper grid.

Polarized light microscopy (PLM) was performed on an Olympus BX-51 coupled with a Mettler-Toledo hot stage FP-90. The image was captured using an Insight digital camera. Isothermal characterization was carried out by preheating gratings on a hotplate at 90°C then transferred to a Mettler Toledo hotstage for observation.

Optical characterization of the reflection gratings was carried out using an Ocean Optics fiber spectrometer. A white light source coupled to a fiber-optic delivery system was used as the light source.

2D SAXS experiments were carried out at the synchrotron X-ray beamline X-27C at the National Synchrotron Light Source in Brookhaven National Laboratory. The zero pixel of the 2D SAXS pattern was calibrated using silver behenate with the first-order scattering vector q being 1.076 nm^{-1} . The air scattering was subtracted. The X-ray beam spot was 0.1 mm in diameter. The X-ray beam was aligned parallel to the *surface* and *normal* directions of the sample. 2D WAXD

patterns were also recorded at room temperature in the same set up with the sample to detector distance of ~ 15 -19 cm.

RESULTS & DISCUSSION:

Temperature sensitive Bragg grating from PEG/Norland

A 1D BR was written using a single beam configuration as previously discussed. Figure 2a shows the transmission spectra of PEG/Norland grating with different Mw. Reflection peaks with modest diffraction efficiency ($\sim 30\%$) can be seen. The notch position is ~ 600 -610 nm, which can be tuned by changing the incident angles of the set-up. The formation of DE indicates a RI modulation in the BR, which is due to the spatial distribution of crosslinked photopolymer and PEG. Thin cross sections (~ 60 nm thick) were obtained by ultramicrotoming along the film normal direction at room temperature. Figure 2b shows a TEM micrograph of a thin section of the grating of Norland 65 and PEG2000. Similar to previously reported PEG 4600/Norland 65 sample, a long range uniform layered structure, with alternating dark and light regions is evident from the micrograph. Unlike holographic polymer dispersed liquid crystal systems, which form droplets of 100-200 nm in diameter confined within the polymer matrix, the PEG layers form a continuous layered structure with a lamellar spacing of ~ 200 nm. The unique morphology may be due to a slower phase separation process of PEG and Norland during polymerization as opposed to LC/Norland systems.

In the previous study, the notch position as well as the DE of these HPDP films could be modulated by varying the temperature: as the temperature increases, both the notch position and the DE increase and the reverse occurs upon cooling.⁽¹⁹⁾ This is due to PEG going through a crystal-melt transition, the volume increases and the BR grating expands, which in turn, leads to

a red shift of the notch as observed in the transmission spectra. Furthermore, the refractive index of PEG is smaller in the amorphous state. Since the RI of the Norland resin is higher than that of PEG, decreasing PEG RI leads to an increase of the RI contrast between the Norland resin and the PEG layer; this dramatically increased the DE of the BR. The melting points of the PEG crystal depends on the polymer molecular structure such as Mw leading to the speculation that different Mw PEG BR might have different thermoswitching temperatures.

In order to confirm this hypothesis, three different Mw PEG samples were used for the thermal switching experiments. Figure 3 shows the notch/DE vs. temperature plots for PEG2000/Norland, PEG4600/Norland, and PEG8000/Norland systems. Figures 3a, c and e exhibit the characteristic red shift and increase in DE during the heating cycle while Figure 3b, d and f show the reverse effects of the cooling process. The transition temperatures can be identified as 46 °C, 50 °C and 57 °C upon heating PEG2000/Norland, PEG4600/Norland, and PEG8000/Norland samples. Upon cooling, PEG4600/Norland and PEG8000/Norland showed 30 °C and 35 °C transitions. The various switching temperatures can be attributed to the different melting points of the PEG/Norland gratings. The PEG2000/Norland BR cooling curve shows that the notch position and DE do not have a sharp change, but a gradual decrease in DE and notch position. This is attributed to the slow crystallization kinetics of the PEG 2000 in the HPDP at room temperature. Therefore, a thermosensitive BR with the switching temperatures ranging from 30 °C to 57 °C can be readily obtained.

Transmission grating based on PEG and Norland resin was also achieved using the set-up previously discussed and the DE was measured to be ~ 1.5%. The Bragg diffraction angle was ~ 46°, leading to a d-spacing of 439 nm, which was confirmed by the SEM results. Figure 4 shows a SEM micrograph of the surface of transmission grating of PEG400 (19%)/Methanol

(10%)/Norland 107 (68 %)/ Darocure© 4265 (3%). Methanol was added to decrease the system viscosity. 1D layer structure can be seen from the figure, indicating that PEG was patterned using the H-P technique with the transmission grating geometry (note that this sample was not microtomed). The transmission grating shows the buckling effect along the layer direction, this may be attributed to the shrinkage of the grating structure after methanol evaporated. A detailed study is ongoing to quantitatively understand the relationship between the buckling and the methanol contents.

PEG phase structure and morphology in the confined HPDP

Since PEG molecules are confined within the crosslinked Norland resin layers, the present BR also provides an excellent system to study the confined crystallization behavior of PEG. Synchrotron X-ray diffraction and PLM experiments were employed. The HPDP cell was opened using a razor knife and thin, free-standing films ($\sim 10 \mu\text{m}$) were obtained. This film was subjected to 2D XRD studies. Figure 5 shows the XRD pattern of PEG/Norland BRs with X-ray aligning parallel (Figure 5a, c, e and g), and perpendicular (Figure 5b, d, f and h) to the gratings, respectively. Figure 5a and b are schematic representations of the experimental set-up. In Figure 5c, e and g the XRD patterns show orientation while in Figure 5d, f and h only ring patterns were obtained. Detailed investigation determined that the inner diffraction arcs can be assigned as (120) with a d-spacing of 0.493 nm and the outer diffraction can be assigned as the overlap of (-132), (032), (112), (-212), (124), (-204), and (004) reflections with a d-spacing of 0.396 nm. In Figure 5c, e and g it is clear that the (120) diffractions are located on the meridian direction while the outer (-132), (032), (112), (-212), (124), (-204), and (004) reflections are located in the quadrants, as shown in the azimuthal scan (Figure 6). Note that in the parallel alignment, the BR

film is parallel to the X-ray and the meridian direction; all the (120) planes are parallel to the equator of the XRD pattern. While the unorientated diffraction patterns in the perpendicular set-up indicate that the PEG crystals do not have any in-plane orientation. Combining these two diffraction patterns, one can conclude that in the patterned regions of the HPDP, PEG forms lamellar crystals and all the PEG chains are perpendicular to the HPDP BR surface.

Figure 7 shows the PLM observation of the PEG HPDD structures. All the polymers were dissolved in the monomer syrup before writing (for PEG 8000, heating was applied to ensure the homogeneous syrup); solidification/crystallization occurs during/after polymerization. It was observed that for the as-written samples, both the grating region and the unpatterned region show grainy texture while the grating areas have much lower birefringence. After melt and recrystallization, 2D spherulitical growth was observed in both sections, and the unpatterned region retains a higher birefringence than the patterned area. Multilayer growth can be observed in the grating as shown in Figures 7 (arrows). This may be due to the crystal growing in different layers of the grating. The relatively weak birefringence in the patterned region suggests that polymer chains are parallel to the film normal resulting in weak in-plane birefringence. The PLM observation is thus consistent with the XRD results.

Figure 8 shows the schematic representation of the hierarchical structures of the PEG/Norland BR. On the ~60 nm level, lamellar layered structures with two crosslinked Norland layers confining PEG molecules between them provide hard nanoconfinement. Upon crystallization, PEG chains are parallel to the layer normal and the (120) planes are perpendicular to the layer surface. Confinement growth of polymer single crystal has been extensively studied in block copolymer systems. Crystal orientation was observed to depend upon the crystallization conditions and the same crystal orientation was observed for

recrystallizing PEO-b-PS sample ($M_n^{\text{PEO}} \sim 8.7\text{K}$ and $M_n^{\text{PS}} \sim 9.2\text{K}$) at temperatures higher than $35\text{ }^\circ\text{C}$.⁽²⁰⁾ The lamellar periodicity is $\sim 18.7\text{ nm}$. In the present case, the HPDP structure possesses a much larger scale compared to the previous block copolymer systems, indicating the nanoconfinement effect can also be observed at $\sim 60\text{ nm}$ scale. Furthermore, the PEG molecules are not tethered to the Norland matrix. The previous argument regarding the tethered junction of BCPs could induce a near perpendicular orientation to the inter-material dividing surface can be excluded in the present case. The perpendicular chain orientation of the PEG crystal appears to be a thermodynamically more stable state. The in-plane orientation of the PEG allows the $\langle 120 \rangle$ direction of the PEG to be parallel with the HPDP surface, leading to much larger, more stable polymer crystals. In contrast, tilted or parallel chain orientation would lead to a $\langle 120 \rangle$ direction that is oblique/perpendicular to the HPDP surface, the crystal would quickly meet the solid confinement wall of the HPDP. Large size crystals are thus prohibited, which in turn, reduce the overall stability of the crystals. Thus, nanoconfinement effect on PEG crystallization was confirmed in the current HPDP system.

CONCLUSION:

BR structures were fabricated using holographic polymerization of several PEG/ Norland systems. Uniform lamellar structures were formed with periodicity $\sim 200\text{ nm}$. The RI modulation between Norland resin and PEG led to the observation of a reflection notch in the transmission spectra. The notch position and the DE can be thermally shifted. The switching temperature was determined by the melting and crystallization temperature of PEG. In addition, the switching

temperature was also be tuned by using different Mw PEGs; switching temperatures from 30 °C to 57 °C were obtained. Both reflection and transmission grating structures were achieved. The hierarchical structure of the BR and PEG crystal were studied using synchrotron X-ray and the PEG crystal lamellae were parallel to the BR surface and the chain axis was parallel to the BR normal. Compared to the confined crystallization of PEO studied in the block copolymer cases, the current system possesses larger nanodomain thickness and the PEG chains are not tethered to the interface. The orthogonal orientation of the lamellae is attributed to the thermodynamic stable state of the crystal.

ACKNOWLEDGEMENTS:

MJB would like to thank NSF-IGERT Fellowship (DGE-0221664) and Sigma Xi Grants-in-Aid of Research (G200510101920132434) for their support. This work is supported by the NRC/US AFOSR Summer Faculty Fellowship and NSF CAREER Award (DMR-0239415). CYL thanks the Mettler-Toledo Co. for the Turi Award supporting the thermal analysis equipment purchase. Synchrotron experiments were conducted at beamline X27C, NSLS in Brookhaven National Laboratory supported by DOE.

REFERENCE:

1. Joannopoulos JD, Villeneuve PRF, H. FS. 1997. *Nature* 386: 143-9
2. Xia YN, Gates B, Yin YD, Lu Y. 2000. *Adv. Mater.* 12: 693-713
3. Foulger SH, Kotha S, Seryda-Krawiec B, Baughman TW, Ballato JM, et al. 2000. *Optics Lett.* 25: 1300-2
4. Fink Y, Urbas AM, Bawendi MG, Joannopoulos JD, Thomas EL. 1999. *J. Lightwave Technol.* 17: 1963-9
5. 2001. *Adv. Mater. Special issue* 13: 369-450
6. Morkved TL, Lu M, Urbas AM, Ehrichs EE, Jaeger HM, et al. 1996. *Science* 273: 931-3.
7. Angelescu DE, Waller JH, Adamson DH, Deshpande P, Chou SY, et al. 2004. *Adv. Mater.* 16: 1736
8. Kim SO, Solak HH, Stoykovich MP, Ferrier NJ, de Pablo JJ, Nealey PF. 2003. *Nature* 424: 411-4.
9. Stoykovich MP, Muller M, Kim SO, Solak HH, Edwards EW, et al. 2005. *Science* 308: 1442-6
10. Bunning TJ, Natarajan LV, Tondiglia VP, Sutherland RL. 2000. *Ann. Rev. Mater. Sci.* 30: 83-115
11. Colburn WS, Haines KA. 1971. *Appl. Optics* 10: 1636-41
12. Gambogi WJ, Weber AM, Trout TJ. 1994. *SPIE Proc.* 2043: 2-13
13. Smothers WK, Moroe BM, Weber AM, Keys DE. 1990. *SPIE Proc.* 1212: 20-9

14. Tondiglia VP, Natarajan LV, Sutherland RL, Tomlin D, Bunning TJ. 2002. *Adv. Mater.* 14: 187-91
15. Campbell M, Sharp DN, Harrison MT, Denning RG, Turberfield AJ. 2000. *Nature* 404: 53-6
16. Sutherland RL, Tondiglia VP, Natarajan LV, Chandra S, Tomlin D, Bunning TJ. 2002. *Optics Express* 10: 1074-82
17. Escuti MJ, Qi J, Crawford GP. 2003. *Optics Letters* 28: 522-4
18. Vaia RA, Dennis CL, Natarajan LV, Tondiglia VP, Tomlin DW, Bunning TJ. 2001. *Adv. Mater.* 13: 1570-4
19. Li CY, Birnkrant MJ, Natarajan LV, Tondiglia VP, Lloyd PF, et al. 2005. *Soft Matter* 1: 238-42.
20. Zhu L, Cheng SZD, Calhoun BH, Ge Q, Quirk RP, et al. 2000. *J. Am. Chem. Soc.* 122: 5957-67

Fig. 1 Experimental set-up for one prism: (a) reflection grating and (b) transmission grating writing.

Fig. 2 (a) Transmission spectra of the reflection gratings of PEG and Norland 65 adhesives. The baselines have been offset for clarity in display of the spectra. (b) TEM micrograph of a thin section of a PEG 2000/ Norland 65 reflection grating.

Fig. 3 Plots of the notch position and DE change with respect to temperature in transmission spectra of the PEG/Norland 65 systems: (a) PEG 2000/Norland 65 on heating; (b) PEG 2000/Norland 65 on cooling; (c) PEG 4600/Norland 65 on heating; (d) PEG 4600/ Norland 65 on cooling; (e) PEG 8000/Norland 65 on heating; (f) PEG 8000/Norland 65 on cooling.

Fig. 4 SEM micrograph of the surface of a PEG/Norland transmission grating.

Fig. 5 2D X-ray pattern of PEG/Norland grating.: (a) X-ray set-up for parallel setting; (b) X-ray set-up for perpendicular setting; (c) 2D X-ray pattern for parallel setting PEG 2000/Norland; (d) 2D X-ray pattern for perpendicular setting PEG 2000/Norland; (e) 2D X-ray pattern for parallel setting PEG 4600/Norland; (f) 2D X-ray pattern for perpendicular setting PEG 4600/Norland; (g) 2D X-ray pattern for parallel setting PEG 8000/Norland; (h) 2D X-ray pattern for perpendicular setting PEG 8000/Norland;

Fig. 6 Azimuthal scan of the 2D XRD patterns in Figure 5: (a) perpendicular setting PEG /Norland, first ring d-spacing = 0.498 nm; (b) perpendicular setting PEG /Norland, second ring d-spacing = 0.396 nm; (c) parallel setting PEG /Norland, first ring d-spacing = 0.498 nm; (d) parallel setting PEG /Norland, first ring d-spacing = 0.396 nm.

Fig. 7 PLM micrograph of PEG 4600/Norland/ BR: a) grating area and b) non grating area.

Fig. 8 Schematic representation of the hierarchical structure of PEG/Norland BR: (a) lamellar structure are formed with a periodicity of ~200 nm; (b) with in the PEG layers, PEG crystals are

formed and the lamellar crystals are parallel to the BR surface and the PEG chains are parallel to the BR normal.

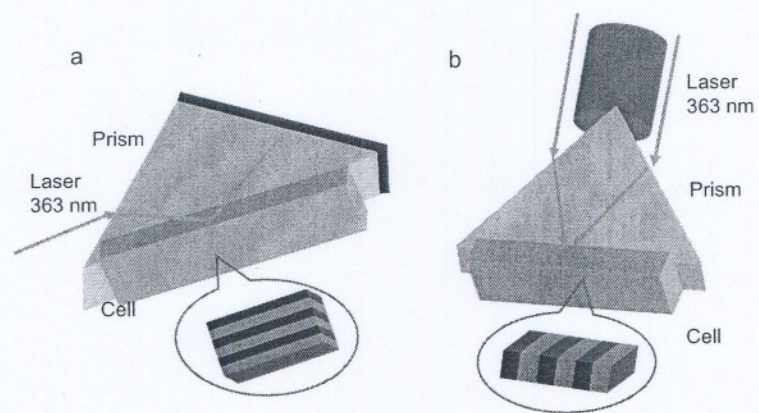


Figure 1

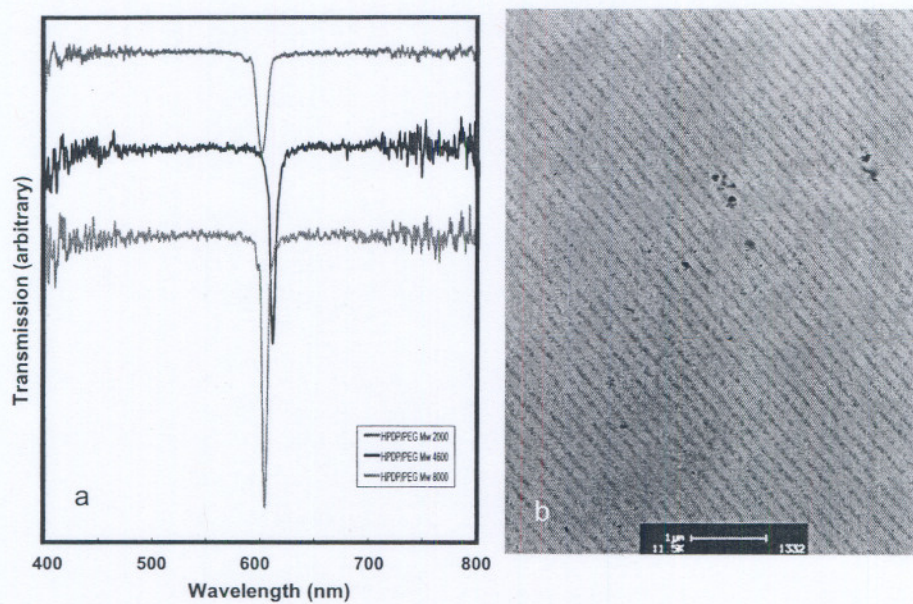


Fig 2

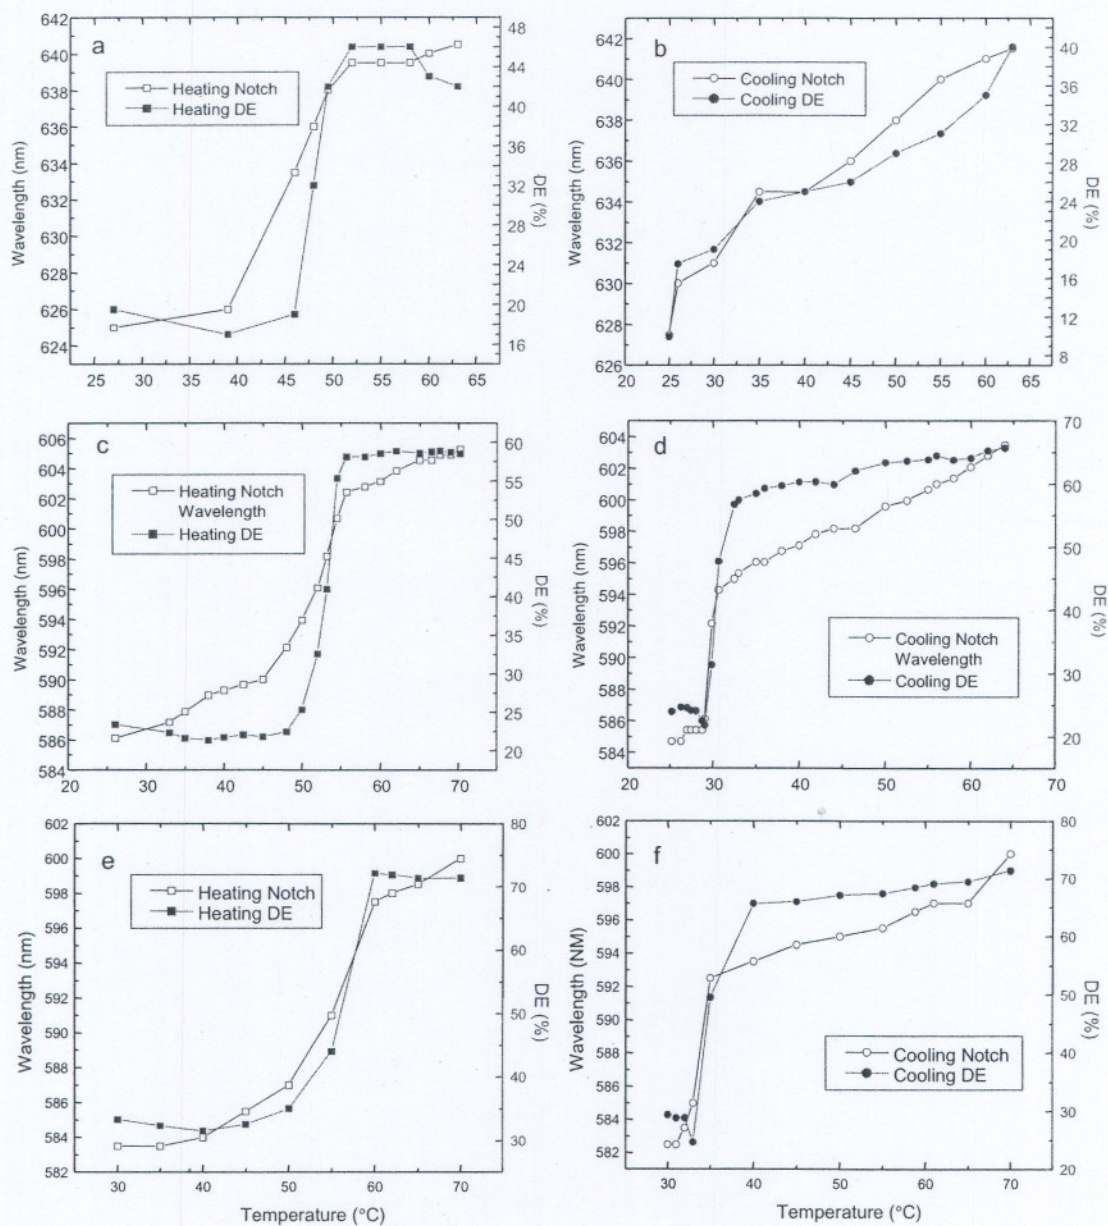


Fig. 3

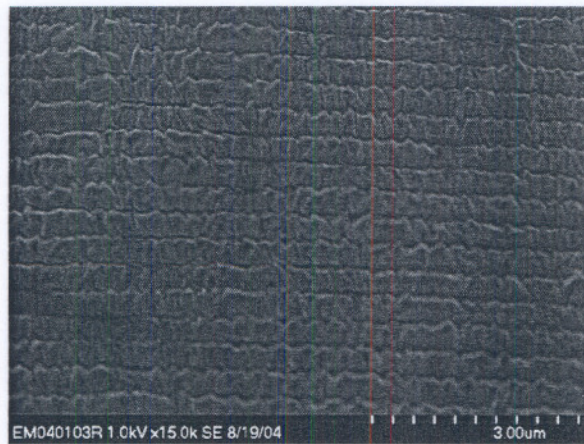


Fig. 4

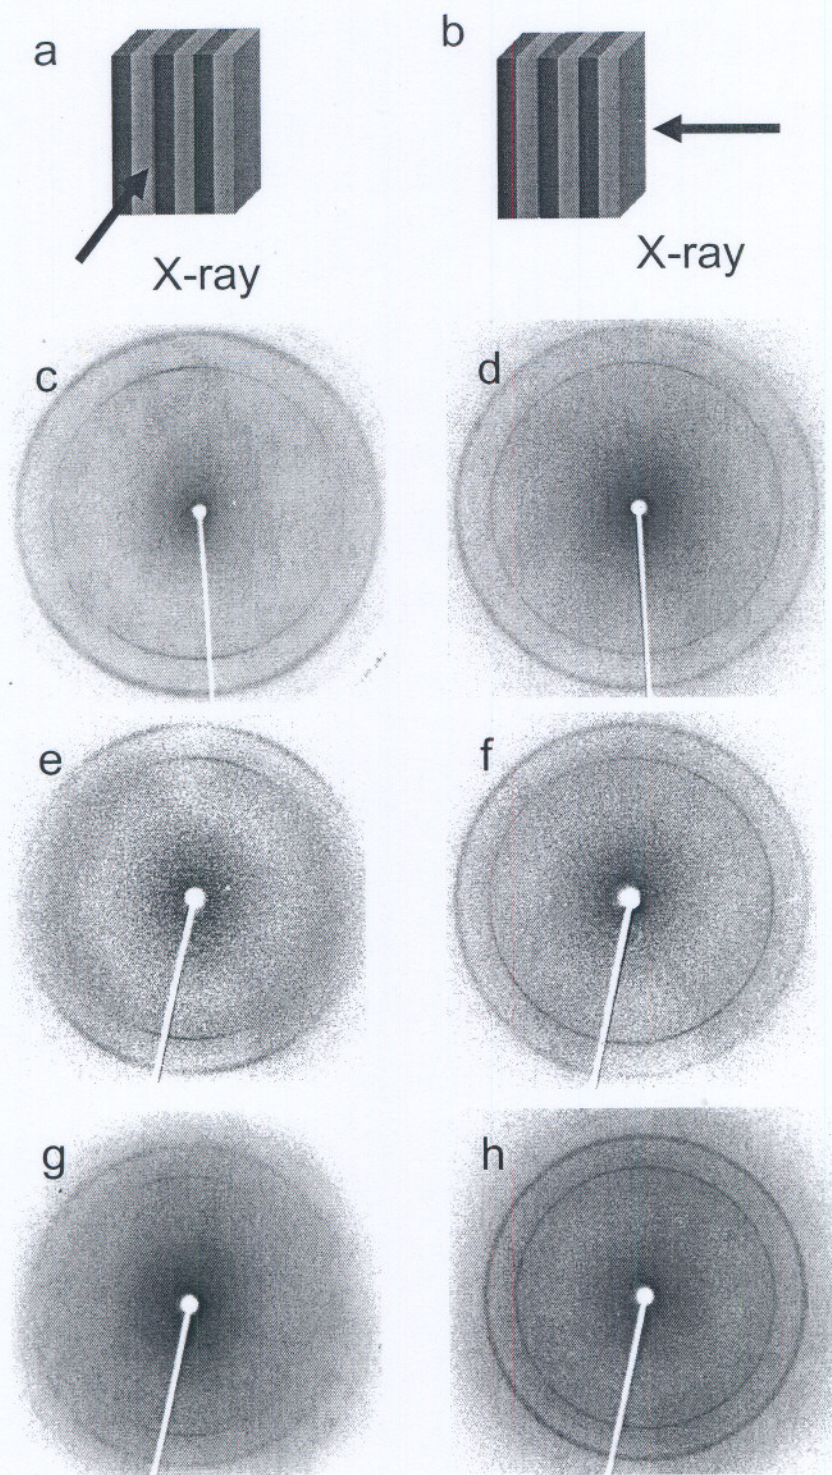
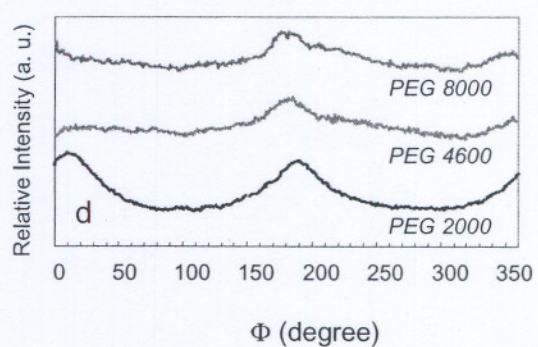
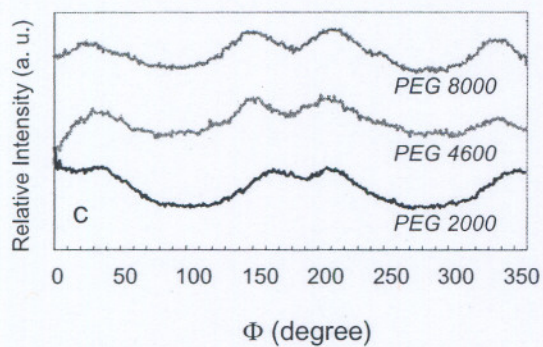
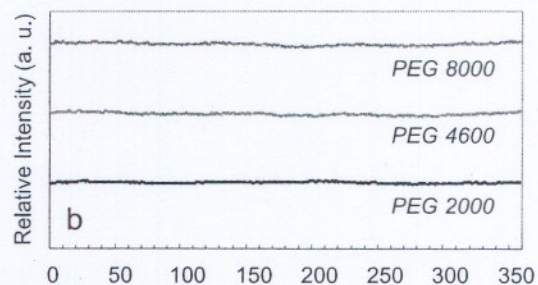
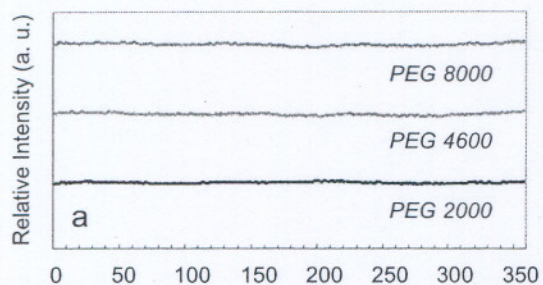


Fig. 5



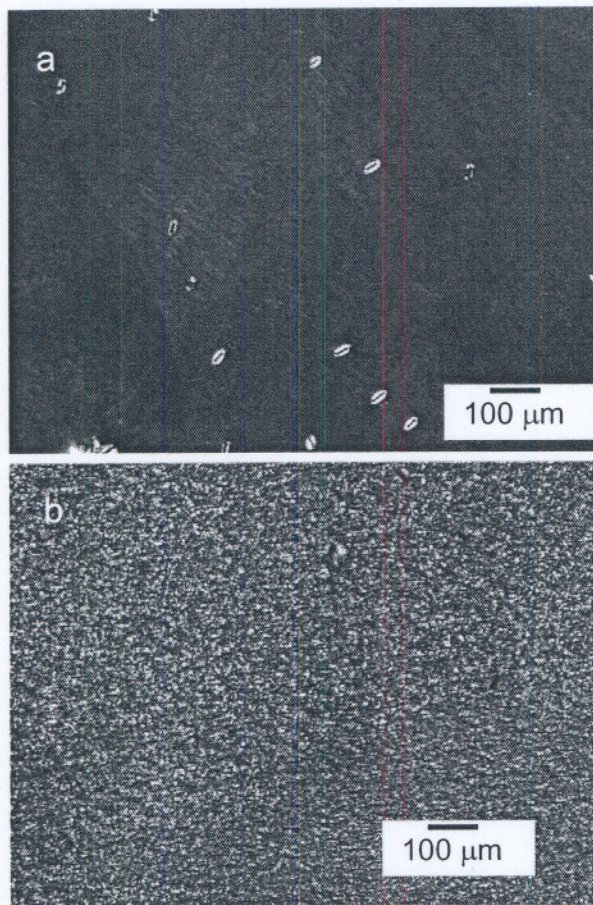


Fig7

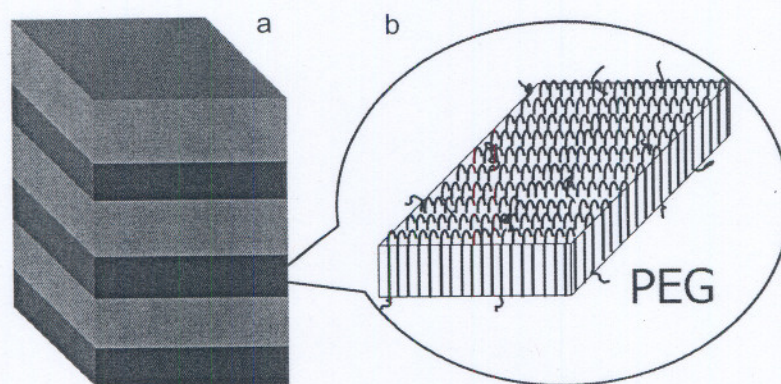


Fig. 8